

Comparative Study in Between Two Types of Fibres for Mechanical Behavior of High Strength Fibre Reinforced Concrete Fibre Reinforced Concrete

Abhijeet P. Wadekar, Rahul D. Pandit

Abstract: The use of High Strength Concrete (HSC) is incérasse rapidly. From the study of expérimental investigation, It has been observe that HSC is relatively brittle material. Fibres are added to improve its ductility. Experimental study is carried out to assess comparative study in between two types of fibres for mechanical properties of high strength fibre reinforced concrete (HSFRC) of grade M80. In addition to normal materials, silica fume, fly Ash and two types of fibres viz. polypropylene fibre and sound crimped steel fiber, are used. The content of silica fume and fly ash is 5% and 10% respectively by weight of cement. Water to cementitious material ratio was 0.25. Mixes are produced by varying types of fibres and for each type of fibre its volume fraction is varied from 0.5% to 4.0 % with an increment of 0.5% by weight of cementitious materials. 51 specimens each of cubes (100 × 100 × 100mm), cylinders (100 × 200mm) and prisms (100 × 100 × 500mm) are tested to study the effect type and volume fraction of fibres on compressive strength, split tensile strength and flexural strength of HSFRC. The results indicated significant improvement in mechanical properties of HSFRC.

Keywords– Polypropylene Fibres, sound crimped steel fiber, High Strength Fibre Reinforced Concrete, Compressive Strength, Split Tensile Strength, Flexural Strength

I. INTRODUCTION

Concrete is a man made rocks which commonly used as construction material. It traditionally consists of cement, fine aggregate, coarse aggregate and water. However modern concrete is produced by adding mineral and chemical admixtures also. IS 456-2000 suggested the use of fly ash, silica fume, ground granulated blast furnace slag (ggbs), metakaoline, rice husk ash (RHA) in the production of concrete. Concrete has been categorized as ordinary, standard and high strength based on characteristic compressive strength at the age of 28 days. High strength concrete is being produced due to growing demand for taller and larger structures. As per IS 456,

High strength concrete is a concrete with strength between 60 to 80 MPa. Such a concrete demands the use of supplementary cementitious materials (SCM) and super plasticizer in order to reduce cement consumption, increase strength, decrease permeability, and improve durability. It is noticed that high strength concrete is a relatively brittle material possessing lower tensile strength.

Internal micro cracks are inherently present in the concrete and its poor tensile strength is due to the propagation of such micro cracks, eventually leading to brittle fracture of the concrete. It has been recognized that the addition of small, closely spaced and uniformly dispersed fibres in the concrete would act as crack arresters and would substantially improve its flexural strength. The toughness of HSFRC depends upon the percentage content of silica fume, fly ash, type of fibre, its volume fraction and aspect ratio.

Such a concrete is in demand wherein resistance to cracking is a performance requirement of the structure e.g. liquid storage tanks.

II. LITERATURE REVIEW

Various researchers have carried out experimental investigation to study the mechanical behaviour of high strength fibre reinforced concrete. The markable investigation carried out on mechanical properties of high strength fibre reinforced concrete (HSFRC) by P.S.Song and S. Hwang that the brittleness with low tensile strength and strain capacities of high strength concrete (HSC) can be reduce by the addition of steel fibres [1]. It is reported that the use of steel fibres in concrete decrease the workability of concrete but increase split tensile strength, flexural strength, modulus of elasticity and poissons ratio [3,4]. P.Balaguru and Mahendra Patel studied the flexural toughness of steel fibre reinforced concrete by using deformed and hooked end fibres. The results indicated that hooked end fibres provided better results than deformed fibre [5]. The experimental investigation is carried out to study the influence of fibre content on the compressive strength, modulus of rupture, toughness and splitting tensile strength [6,7,12]. S.P.Singh and S.K.Kaushik carried out an experimental program to study fatigue strength of steel fibre reinforced concrete (SFRC), in which they obtained the fatigue-lives of SFRC at various stress level and stress ratio.

Revised Manuscript Received on 30 November 2014.

* Correspondence Author

Dr. Abhijeet P. Wadekar*, People's Education Society's, P. E. S. College of Engineering, Aurangabad, Maharashtra, India.

Prof. Rahul D. Pandit, Faculty of CSMSS's, Chh. Shahoo College of Engineering, Kanchanwadi, Aurangabd, Maharashtra, India.

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](http://creativecommons.org/licenses/by-nc-nd/4.0/) article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>

Comparative Study in Between Two Types of Fibres for Mechanical Behavior of High Strength Fibre Reinforced Concrete

There results indicated that the statistical distribution of equivalent fatigue-life of SFRC is in agreement with the two-parameter Weibull distribution. The coefficient of the fatigue equation were determined corresponding to different survival probabilities so as to predict the flexural fatigue strength of SFRC for the desired level of survival probability [9].

The use of mineral admixtures such as silica fume and fly ash in high strength concrete gives the smaller paste porosity as compared to controlled concrete which increases the compressive strength, split tensile strength and flexural strength [10, 11, 13, 14, 17]. The production of good concrete can be done using automation and controlled environment but it not possible to alter its inherent brittle nature and the lack of any tensile strength. The addition of polypropylene fibres in plane concrete, it has increased the ductility and energy absorption capacity of concrete [18]. In the present investigation mechanical behaviour of HSFRC is studied by incorporating various types of fibres.

III. NEED FOR INVESTIGATION

The higher compressive strength and ductility are the most important parameters in the design of RCC structures. However, it is observed that ductility of concrete reduces with higher compressive strengths. Inclusion of fibres may arrest the cracks and improve tensile strength of concrete and thus ductility.

IV. OBJECTIVES AND SCOPE

The investigation is focused to study the effect of various types of fibres on compressive strength, split tensile strength and flexural strength of HSFRC. The water to cementitious material ratio considered for the study of HSFRC of M80 grade was 0.25. The content of silica fume and fly ash in every mix was 5% and 10% by the weight of cementitious material. Two types of fibres considered for the study include, Polypropylene Fibres (PF) and Sound Crimped Steel Fibres (SCSF). Dosage of fibre was varied from 0.5% to 4% at an interval of 0.5% by weight of cementitious material. Type of cement, fine aggregate, coarse aggregate, type of superplasticiser and its dosage are kept constant in every mix.

V. EXPERIMENTAL PROGRAM

There are 8 mixes cast using single type of fibre. Thus there are in all 16 mixes cast using six types of fibres. The details of the experimental programme are given in Table 2.1

Table 2.1: Schedule of Experimental Program

Sr. No.	Mix designation of M80 grade HSFRC	Fibre content (%)	No. of specimen (cubes, cylinders and prisms each) using types of Fibres	
			PF	SCSF
1	M0	0.0	3	
2	M1	0.5	3	3
3	M2	1.0	3	3

4	M3	1.5	3	3
5	M4	2.0	3	3
6	M5	2.5	3	3
7	M6	3.0	3	3
8	M7	3.5	3	3
9	M8	4.0	3	3

VI. MATERIALS

Ordinary Portland Cement of 53 Grade conforming to IS: 12269-1987 was used in the investigation. The properties of cement are presented in Table 2.2.

Table 2.2: Physical Properties of Ordinary Portland cement (OPC)

Sr. No.	Description of Test	Results
01	Fineness of cement (residue on IS sieve No. 9)	6%
02	Specific gravity	3.15
03	Setting time of cement a) Initial setting time b) Final setting time	118 minute 322 minute
04	Soundness test of cement (with Le-Chatelier's mould)	1mm
05	Compressive strength of cement (a) 3 days (b) 7 days (c) 28 days	41.03 N/mm ² 55.44 N/mm ² 77.82 N/mm ²

Crushed stone metal with a maximum size of 12.5 mm from a local conforming to the requirements of IS: 383-1970 was used. Locally available river sand passing through 4.75 mm IS sieve conforming to grading zone-II of IS: 383-1970 was used. The properties of aggregates are presented in Table 2.3

Table 2.3: Physical Properties of Fine and Coarse Aggregate

Sr. No	Property	Results	
		Fine Aggregate	Course aggregate
1.	Particle Shape, Size	Rounded, 4.75 mm down	Angular, 10mm down
2.	Fineness Modulus	2.38	6.87
3.	Silt content	2%	
4.	Specific Gravity	2.624	2.684
5.	Bulking of sand	4.16%	0.4%
6.	Bulk density	1586.26 kg/m ³	1565 kg/m ³
7.	Surface moisture	Nil	Nil

Sulphonated melamine based super plasticizer supplied by Roff. Chemicals India Pvt. Ltd. Mumbai is used as water reducing and self retarding admixture in the experimental work. The properties comply with the requirements of IS 9103-1999 (Amended 2003) as well as ASTM C 494-type F.

The fly ash are used which available from Nashik. The specific gravity of fly ash was 2.3. The properties of fly ash are presented in Table 2.4

2.4: Physical Properties of Fly Ash

Sr. No.	Description of Test	Results
01	Specific Gravity	2.3
02	Colour	Grayish white
03	Bulk Weight	Approx. 0.9 metric ton per cubic meter
04	Specific density	Approx. 2.3 metric ton per cubic meter
05	Average Particle size	0.14mm
06	Particle shape	Spherical

The properties of various types of fibres considered for the study are presented in Table 2.4

Table 2.4: Properties of Fibres used

Sr. No.	Property	Properties of two types of fibres	
		PF	SCSF
2.	Length (mm)	40	30
3.	Width (mm)	1.20	-
4.	Diameter (mm)	0.50	0.45
6.	Aspect Ratio	-	66.66
7.	Colour	White	White
8.	Specific Gravity	0.9	7.85
9.	Density kg/m ³	1.36	1.36
10.	Tensile strength MPa	400-800	400-1000
11.	Melting point	253 °C	253°C
10	Young's modulus kN/mm ²	11.3	25.19
13.	Water absorption	0.04%	0.04%
14.	Minimum elongation	8%	8%
15.	Resistance to alkali in high strength concrete	Excellent	Excellent
16.	% Elongation	8	8
17.	Effective Diameter mm	0.874	0.456

VII. PRODUCTION OF HSFRC CONCRETE

The high strength concrete of M80 grade was designed as per DOE method. Table 2.5 shows the weights of various constituents of HSFRC.

Table 2.5: Mix Proportion

Sr. No	Material	Weight of material in Mass kg/m ³
1	Ordinary Portland Cement (85 % of CM)	472.6
2	Silica fume (5 % of CM)	27.8
3	Fly Ash (10 % of CM)	55.6
4	Fine Aggregate	702
5	Coarse Aggregate	1042
6	Water	150

7	Superplasticizer	18 ml per kg of Cement
8	Water Binder Ratio	0.25

VIII. RESULT AND DISCUSSION

The discussion on each result is presented in the following sections

A. Effect of fibres content (%) on Compressive Strength of High Strength Concrete


The effect of Silica fume, fly ash and the two types fibres on compressive strength of concrete as shown in figure 3.1. The fibre volume fraction is indicated on X-axis and compressive strength is on Y-axis. The compressive strength increases significantly due to the addition of fibres compared with normal high strength concrete. In general, the compressive strength of the concrete having Polypropylene fibre was higher than that of concrete with sound crimped steel fibres at the same volume fractions of fibres up to the limit. The compressive strength of concrete with all fibres is increased up to the 3 % of fibres volume fraction and then decreases. The maximum values of compressive strength at 3 % fibres volume fraction are 97 N/mm² and 87.5 N/mm² for PF and SCSF respectively.

B. Effect of fibres content (%) on Split Tensile Strength of High Strength Concrete

The effect of Silica fume, fly ash and two types of fibres on split tensile strength of a high strength fibres reinforced concrete has been shown in figure 3.2. The fibre volume fraction is indicated on X-axis and split tensile strength is on Y-axis. The result from Table 2.4 shows that the cylinder split tensile strength of concrete increases considerably with an increase in fibres content. A continuous increase in strength is observed up to a limit. The 3 % of fibres content has given maximum increase in split tensile strength as compared to that of normal concrete. Polypropylene fibre was higher than that of concrete with Sound crimped steel fibres at the same volume fractions of fibres up to the limit maximum split tensile strength of 7.21N/mm².

C. Effect of fibres content (%) on Flexural Strength of High Strength Concrete

The effect of Silica fume, fly ash and two types of fibres on flexural strength of a high strength fibres reinforced concrete has been shown in figure 3.3. The fibre volume fraction is indicated on X-axis and flexural strength is on Y-axis. The result from Table 2.4 shows that the prism flexural strength of concrete increases considerably with an increase in fibres content. A continuous increase in strength is observed up to a limit. The 2.5 % and 3.0% of fibres content has given maximum increase in flexural strength as compared to that of normal concrete. The with Sound crimped steel fibres gives maximum split tensile strength of 19.56N/mm² than that of Polypropylene fibre of Fibres.

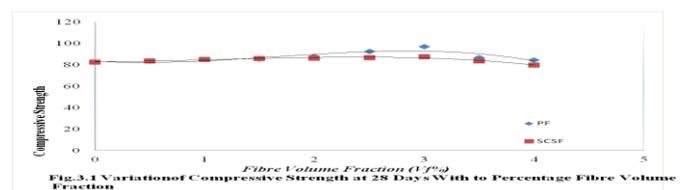


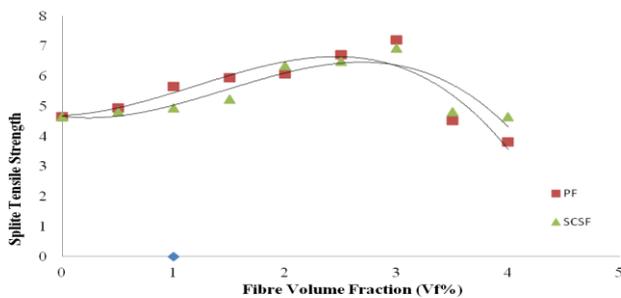


Fig 3.2 Variation at Split Tensile Strength at The Age of 28 days With Respect to Percentage Fibre Volume Fraction

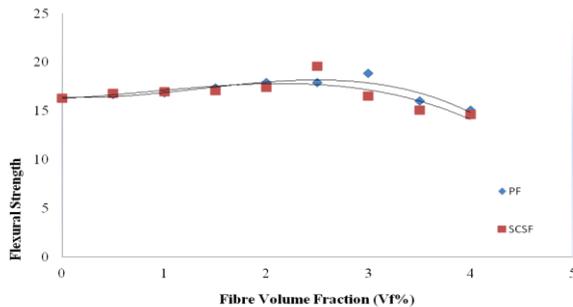

Variation of Flexural Strength at 28 Days With Respect to Percentage Volume Factor

IX. CONCLUSION

From the results discussed in the previous section, following conclusions are drawn.

- 1) HSC without fibres is relatively brittle and fails suddenly when compared with HSFRC with different types of fibres.
- 2) The compressive strength of HSC improves with addition of fibres. The maximum strength was occurred at 3% of volume fraction of each fibres. The obtained strength for two types of fibres viz. polypropylene fibre and sound crimped steel fiber is as follows i.e 97.00 and 87.50. From the results the higher compressive strength is obtained 97.00 Mpa for polypropylene fibre.
- 3) The split tensile strength of HSC improves with addition of fibres. The maximum strength was occurred at 3% of volume fraction of each fibres. The obtained strength for two types of fibres viz. polypropylene fibre and sound crimped steel fiber is as follows i.e 7.21 and 6.94. From the results the higher compressive strength is obtained 7.21 Mpa for polypropylene fibre fibre.
- 4) The flexural strength of HSC improves with addition of fibres. The maximum flexural strength was occurred at 2.5% of volume fraction of sound crimped steel fiber i.e. 19.56. And 3% of volume fraction of polypropylene fibre is as follows i.e 18.83Mpa. From the results the higher Flexural strength is obtained 19.56 Mpa for sound crimped steel fibre.
- 5) The results obtained in the study are plotted in graphs for each types of test. The study of graph has been concluded that the maximum variations are obtained in split tensile strengths graph as compared to compression and flexural strengths graph.

From this study it is concluded that the use of fibres in HSC can increase the mechanical properties of

HSFRC for split tensile strength as compare to compressive and flexural strength.

REFERENCES

1. P.S.Song., S. Hwang., "Mechanical properties of high strength steel fibre-reinforced concrete", *Construction and Building MATERIALS*, 18 (2004) 669-673
2. S.P.Singh and S.K.Kaushik, "Flexural Fatigue Analysis of steel fibre reinforced concrete", *ACI Material Journal*, Vol.98, No.4, July-August 2001, pp.306-312.
3. Fuat Koksall and Fatih Altun, "Combine effect of Silica fume and steel fibre on the mechanical properties of high strength concrete", *Construction and building materials*, 23(2007), pp.441-454.
4. Job Thomas and Ananth Ramaswamy, " Mechanical Properties of Steel Fibres Reinforced Concrete", *Journal of Materials in Civil Engineering*, May 2007, Vol. 19, No.5, pp.385-392.
5. P.Balaguru, Ramesh Narahari and Mahendra Patel "Flexural Toughness of Steel Fiber Reinforced Concrete", *ACI Materials Journal*, Nov-Dec.1992, Vol.89, No.6, pp.-541-546.
6. Faisal F.Wafa and Samir A. Ashour, "Mechanical Properties of high strength fibre-reinforced concrete", *ACI Materials Journal*, Nov-Dec.1992, Vol.89, No.5, pp.-449-455.
7. Paviz Soroushian and Ziad Bayasi, "Fiber-Type Effect on the Performance of Steel Fiber Reinforced Concrete", *ACI Materials Journal*, March-April.1991, Vol.88, No.2, pp.-291-134.
8. K.H.Tan, P.Paramasivam and K.C.Tan, "Instantaneous and Long-Term Deflection of Steel Fiber Reinforced Concrete Beam", *ACI Structural Journal*, July-August.1994, Vol.91, No.4, pp.-384-393.
9. S.P.Singh and S.K.Kaushik, "Fatigue Strength of Steel Fibre Reinforced Concrete in Flexural", *Cement and Concrete Composites*, 2 September 2002, Vol.25, pp.-779-786.
10. C.S.Poon, S.C.Kou and L.Lam, "Compressive Strength, Chloride Diffusivity and Pore Structure of High Performance Metakaolin and Silica Fume Concrete", *Construction and Building Materials*, August 2005, Vol. 20, pp.-858-865.
11. S.Bhaskar, Ravindra Gettu, B.H.Bharatkumar and M.Neelamegam, "Strength, Bond and Durability Related Properties of Concretes with Mineral Admixtures", *The Indian Concrete Journal*, February 2012, pp.-09-15.
12. Avinash S. Pant and Suresh R. Parekar, "Steel Fibres Reinforced Concrete Beam Without Reinforcement Under Combined Bending, Shear and Torsion", *The Indian Concrete Journal*, April 2012, pp.-39-43.
13. Vivek Bindiganavile, Farnaz Batool and Narayana Suresh, " Effect of Fly Ash on thermal properties of cement based foams evaluated by transient plane heat source", *The Indian Concrete Journal*, November 2012, pp.-7-13.
14. Subhash Mitra, Pramod K. Gupta and Suresh C. Sharma, " Time-dependant strength gain in mass concrete using mineral admixtures", *The Indian Concrete Journal*, November 2012, pp.-15-22.
15. IS: 516-1959, Edition 1.2 (1991-07), "Indian Standard for Methods of test for strength of concrete.
16. Sadr Momtazi A, Ranjbar M. M., Balalaei F, Nemati R, "The effect of Iran's Silica fume in enhancing the concrete compressive strength", *Cement and Concrete Research*, May 2011, pp.-1-7.
17. Jian-Tong Ding and Zonglin Li, " Effect of Metakaolin and Silica Fume on Properties of Concrete", *ACI Material Journal*, July-August 2002, Vol. 99, PP.-. 393-398.
18. Rahul Jain, rishi Gupta, makrand G. Khare and Ashish A. Dharmadhikari, " Use of Polypropylene fibre reinforced concrete as a construction material for rigid pavements", *The Indian Concrete Journal*, March 2011, pp.-45-53.
19. IS: 456-2000, "Indian Standard for code of practice for plain and reinforced concrete".
20. IS: 383-1970. "Specification for coarse and Fine Aggregates from natural sources for concrete." Bureau of Indian standards, New Delhi.