

Surface Roughness Study on Forged Al-TiB₂ Composite by Regression Analysis

Hemavathy S, C N Chandrappa, Prashanth Kumar K C

Abstract: Aluminum composites are very rapidly replacing engineering metals and alloys because of its light weight and high strength in aerospace and biomedical applications etc. In the present work Al-TiB₂ (Aluminum alloy A2024) composite is fabricated by In-Situ technique. The serious examination on impact of surface roughness of Aluminum TiB₂ composite is done. The material is subjected for turning operation to contemplate the surface roughness. This investigation centers around building up an exact model for expectation of surface unpleasantness on manufactured composite. The working parameters are speed, feed, depth of cut and tool nose radius. One of the data mining techniques non-linear regression analysis is applied in developing the empirical model, this model is transferred to software by visual basic programming language.

The test results show that the value of surface roughness is low at high cutting speed and comparatively high at low cutting speed. Surface roughness increases with increase in feed and depth of cut. However it decreases with increasing tool nose radius and surface roughness increases as what% of TiB₂ increases in aluminum. The values of surface roughness of models compared with experimental results. This models developed in this study have a satisfactory compatibility in both model construction and verification and there is a scope for future work.

Keywords: Al 2024 alloy, In-situ technique, surface roughness, regression analysis, tool nose radius.

I. INTRODUCTION

Many of the applications in the world today require material with unusual combinations of properties that cannot be the conventional monolithic materials. This is especially true for materials that are needed for high technology areas such as jet engines, airframes, space shuttles, deep-sea submersibles, hypersonic spacecrafts etc. There is a need of materials having lightweight and high strength, offering a unique combination of properties and to find an extensive application in structural, aerospace and automotive industries. It consists of a homogeneous matrix, particulate reinforced Al-metal matrix composite. In earlier turning tests, it found that tool wear is excessive and surface finish is very poor when carbide tip tools used for machining. For example in grinding wheel on the tool edge is worn out by abrasion leads to poor surface finish. While using MMC specimen it involves consequently friction, high temperature and pressure, particles adhere to cutting tool edge and so called Build-up edge (BUE). When machining also need to

consider wear resistance and fatigue strength. The various roughness parameters are average roughness (R_a), smoothing depth (R_p), root mean square (R_q), maximum peak-to-valley height (R_t). The aim of the present study is to develop the surface roughness prediction model for Al-TiB₂ composite with the aid of a statistical method, using silicon carbide coated tool tip under various cutting conditions (without coolant). Al-TiB₂ is a new material, which belongs to MMC family, which is prepared by in-situ casting. This MMC is likely to have applications in aerospace, marine, and defense, because of its higher specific strength.

Al-TiB₂ composite being another material very little information is accessible on machining the equivalent and it require to streamline the cutting parameters so as to have a good surface finish, which is one of the imperative criteria in aerospace application. Consequently practicality consider on this material has been carried out. Finally building up a scientific model utilizing data mining method, this is usually commonly as nonlinear-regression investigation. The scientific model is exchanged to programming, which can anticipate ideal cutting parameter for surface roughness and the other way around. Further real work machining has been completed to find out the possibility of predator, additionally a similar strategy of building up a surface roughness demonstrate for Al-TiB₂ composite is done after the materials exposed to forging process and the outcomes are analyzed with forged process. It is possible to fabricate Al-TiB₂ composite by in-situ technique and enrichment of TiB₂ particles in Al matrix (2024 alloy). It is observed that surface roughness is low at high speed and comparatively high at low cutting speed; Roughness is low at wt% of TiB₂ and high at higher % of TiB₂ in aluminum.

II. MATERIALS AND METHODS

1. Material compositions: The material used for present work is Al 2024 and TiB₂ are shown in table. Table 1 shows composition of aluminum 2024 alloy according to ASM standards and Table 2 shows properties of TiB₂.

Table 1: Chemical composition of aluminum alloy 2024

	Si	Fe	Cu	Mn	Mg	Cr	Zn	Ti	Others-Each	Others Total	Al
2024	0.50	0.50	3.8-4.9	0.30-0.9	1.2-1.8	0.1-0	0.25	0.15	0.05	0.15	Remainder

Revised Manuscript Received on January 25, 2019..

Hemavathy S, Assistant Professor, Dept. Of Mechanical Engg., RIT, Karnataka, India

Dr C N Chandrappa, Professor and Head, Dept. Of Automobile Engg., Archarya Institute of Technology

Prashanth Kumar K C, Student, Dept. Of Mechanical Engg., RIT, Karnataka, India

Surface Roughness Study on Forged Al-TiB₂ Composite by Regression Analysis

Table 2: Properties of TiB₂

Theoretical density, gm/cm ³	4.52
Melting point °C	2980
Thermal conductivity, W/m-k	25
Hardness, Kg/mm ²	1800-2700
Crystallography	Hexagonal
Color	Gray to dark gray

2. Selection parameters: In the present work experiments are conducted by in-situ technique adapted to regression analysis. The experiments were conducted considering 4 parameters, cutting speed, feed, depth of cut and tool noseradius.

Table 3: Parameters

Sl no	Parameters	Levels	
		1	2
01	Cutting speed	420	1200
02	Feed	0.05	0.11
03	Depth of cut	0.1	0.3
04	Tool nose radius	0.4	0.8

3. Aluminum and its alloys: The important factors in selecting in aluminum and its alloys is their lightweight to high strength, resistance to corrosion by many chemicals, high thermal and electrical conductivity, non-toxicity, reflectivity, appearance, and ease of formality machinability and to benon-magnetic.

Table 4: Properties of various Al alloys at room temperature.

Alloy-Temper	Tensile Strength (ksi)	Yield Strength (ksi)	Elongation (%)
2024-O	17	11	18
2024-T ₃	70	50	16
2024-T ₄	68	47	20

III. METHODOLOGY:

1. In-situ technique: In-situ composites are multiphase materials where the strengthening stage is combined inside the grid amid composite manufacture. In-situ procedure can make an assortment of support morphologies, going from spasmodic to constant, and the fortification might be either flexible or fired stages. For the most part, the fortifications in spasmodically strengthened metallic grid in-situ composites are on the request of 0.5-5 μm, and volume portions go from 0-50 vol. %.


2. Machinability: Machinability alludes to the simplicity with which a metal can be cut allowing the expulsion of the material with an agreeable completion easily. Materials with great machinability require little capacity to cut, can be cut rapidly, effectively get a decent completion, and don't wear the tooling much, such materials are said to be free machining.

Table 5: Materials and their specific machinability ratings

Material	Hardness	Machinability Ratings (%)
6061-T Aluminum	-	190
7075-T Aluminum	-	120
Aluminum	-	120

B1112 Steel	160BHN	100
416 Stainless Steel	200BHN	90
1120 Steel	160BHN	80
1020 Steel	148BHN	65

3. Surface Roughness: The quality of machined surface is characterized by the accuracy of its manufacture with respect to the dimensions specified by the designer. Every machining operation leaves characteristic evidence on the machined surface. This evidence in the form of finely spaced micro irregularities left by the cutting tool. Each type of cutting tool leaves its own individual pattern which therefore can be identified. This pattern is known as surface finish orroughness.

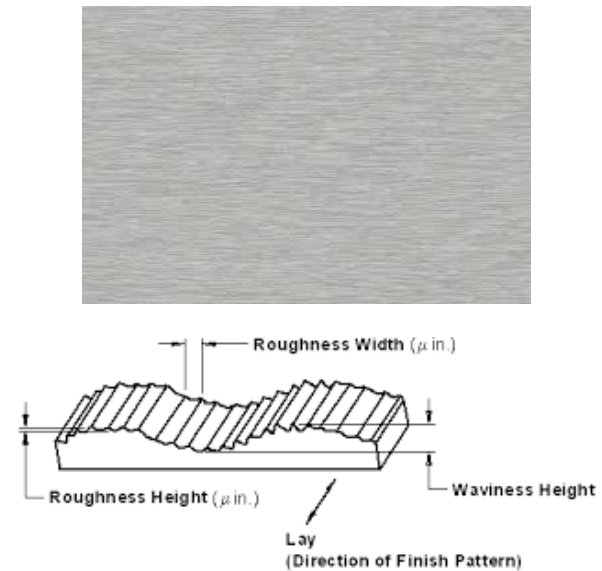

4. Regression Analysis: In statistics, relapse investigation looks at the connection of a reliant variable (reaction variable) to indicated free factors (indicators). The scientific model of their relationship is the regression condition. A regression condition contains appraisals of at least one obscure regression parameters (constants), which are connected to the two factors. Utilization of regression incorporate expectation (counting estimating of time-arrangement information), displaying of causal connections, and testing logical speculations about connections between factors. Relapse examination Software bundles are SAS System, SPSS, Minitab, or stata, perform different kinds of relapse investigation accurately and in an easy to understanding way. In this project work Minitab is used to carry out regression analysis to get the regression equation, which relates cutting parameters (speed, feed, depth of cut, tool radius and %of TiB₂in Aluminum) to predict surfaceroughness.

5. Regression modeling: Afunctionrelationshipbetweensurfaceroughness(Ra)andthe independent variables under investigation is postulated by equation

$$Ra = C t^{a1} s^{a2} f^{a3} d^{a4} r^{a5}$$

Where Ra=surface roughness in micrometer, t=Wt% of TiB₂ in Al composite, s=Cutting speed in rpm,



f=Feed in mm/rev,
r=tool nose radius in mm,
d=depth of cut in mm, C, a₁, a₂, a₃, a₄ and a₅ are constants.

A logarithmic transformation converts the nonlinear form of equation into the following: $\ln Ra = \ln C + a_1 \ln t + a_2 \ln s + a_3 \ln f + a_4 \ln d + a_5 \ln r$

For simplicity, above equation is rewritten as:
 $Y = b_0 + b_1 X_1 + b_2 X_2 + b_3 X_3 + b_4 X_4 + b_5 X_5$

Where Y is the estimated surface roughness value after logarithmic transformation, b₀, b₁, b₂, b₃, b₄ and b₅ are estimates of the parameters respectively. In addition, X₁, X₂, X₃, X₄ and X₅ are the logarithmic transformation of wt% of TiB₂ in Al composite. In the present work constants of above equation is obtained by software called Minitab the levels of each factor are presented in the table 6. As a result, a full factorial design 2⁵ (i.e. 2 stands for two levels, and 5 for five factors) shown in Table 7 is used to facilitate model construction by regression analysis.

Table 6: Factors and levels of experiment for model construction


	Level		Factors		
	% of TiB ₂ in Al composite	Cutting speed in rpm	Feed in mm/rev	Depth of cut in mm	Tool nose radius in mm
	T	S	F	D	R
Low	00.00	420	0.05	0.1	0.4
High	12.00	1200	0.11	0.3	0.8

Table 7: Design of experiments and data for model construction

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius
1	0	420	0.05	0.1	0.8
2	0	420	0.11	0.3	0.8
3	0	1200	0.05	0.1	0.4
4	0	1200	0.11	0.3	0.4
5	12	420	0.05	0.1	0.4
6	12	420	0.11	0.3	0.4
7	12	1200	0.05	0.1	0.8
8	12	1200	0.11	0.3	0.8

6. Development of software for surface roughness prediction: This software is developed by using visual basic programming language for predicting surface roughness for given cutting parameters and vice versa. In the shown fig the window of software, to predict surface roughness of cutting parameters.

Supporting document:

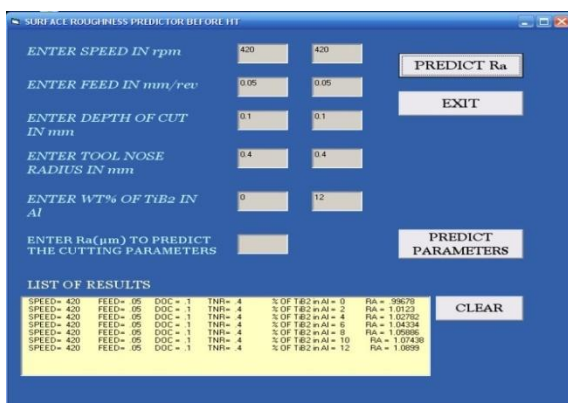

Material preparation:

Aluminium-TiB₂ composite preparation:-

The in-situ composite was made by stir casting technique using the following procedure.

1) Development of software roughness prediction model from regression analysis.

2) Development of software to predict optimum cutting parameter for given surface roughness and surface roughness for the given cutting parameter.

3) Synthesis of TiB₂ by initiating an exothermic reaction in aluminum melt between “Ti” And “B” bearing compounds. Forged Al-TiB₂ enriched composite.

4) Machinability study on Al-TiB₂ composite by varying cutting parameters like speed, feed, Depth of cut, and tool nose radius.

5) Known quantity of Aluminum alloy (Al-2024) was taken in the crucible and kept in the electric furnace for melting.

6) Temperature of the furnace was set at 810°C.

7) The chemical reactants TiO₂, Na₃-AlF₆ and KBF₄ were in the weight ratio of 4:4:1.

8) The quantity of the mixture taken was 2 to 12% by weight of aluminum.

9) The mixture was preheated to 300°C for four hours.

10) The mixture was then slowly added to the liquid aluminum when the temperature of the melt was 810°C.

11) After the addition, the slurry was stirred for a period of about 30min in order that the reaction will occurs.

12) The speed of the stirrer was maintained at 700rpm.

13) After the reaction, the byproducts were skimmed off before pouring.

14) The finger mould and cylindrical mould were coated with chalk powder and preheated for one hour at 300°C.

15) After stirring, melt was kept in furnace for 5 min for reaction to complete.

16) The slurry was poured into the mould at a uniform rate, at room temperature.


17) The castings were removed from the dies after the complete solidification.

Chemical Reactants: The reactants used were:

- 1) Titanium di oxide (TiO₂) particles
- 2) Cryolite (Na₃ AlF₆, i.e. Sodium hexafluoro aluminum) particles
- 3) Potassium tetra fluoroborate (KBF₄)

Typical applications: ceramic sintered parts, structural applications including cutting tool composites, ceramic armor nozzles, wear parts, seals and molten metal crucibles.

Reactions:

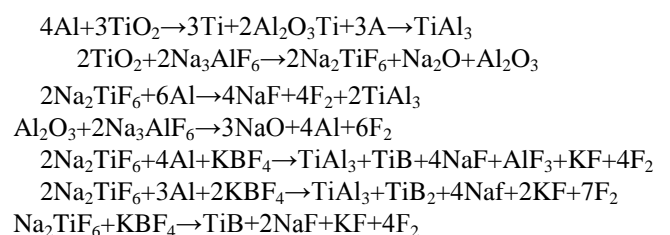

Surface Roughness Study on Forged Al-TiB₂ Composite by Regression Analysis

IV. RESULTS AND DISCUSSIONS:

Influence of cutting parameters on surface roughness predicted by surface roughness model equations:

$$1. Ra = 0.432 + 0.00432T + 0.000456S - 5.14F + 0.029D + 0.341R$$

$$2. Ra = 0.950 + 0.023T + 0.000031S - 3.43F + 0.415D - 0.129R$$

Table 8: Observed and predicted Ra values after forging

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	Predicted Ra	Error	Relative error
1	0	420	0.05	0.1	0.8	0.24	0.39	0.15	38.48
2	0	420	0.11	0.3	0.8	0.46	0.74	0.28	37.83
3	0	1200	0.05	0.1	0.4	0.13	0.73	0.6	82.19
4	0	1200	0.11	0.3	0.4	0.22	0.44	0.22	50
5	12	420	0.05	0.1	0.4	0.23	0.43	0.2	46.51
6	12	420	0.11	0.3	0.4	0.26	0.43	0.17	39.53
7	12	1200	0.05	0.1	0.8	0.20	0.79	0.59	74.68
8	12	1200	0.11	0.3	0.8	0.30	0.50	0.2	40

Table 9: Effect of wt% TiB₂ on surface roughness

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Toolnose radius	Ra
1	0	420	0.05	0.1	0.4	0.21
2	2	420	0.05	0.1	0.4	0.98
3	4	420	0.05	0.1	0.4	0.4
4	6	420	0.05	0.1	0.4	0.78
5	8	420	0.05	0.1	0.4	0.69
6	10	420	0.05	0.1	0.4	0.23
7	12	420	0.05	0.1	0.4	0.23

Fig 1: Effect of wt% TiB₂ on surface roughness

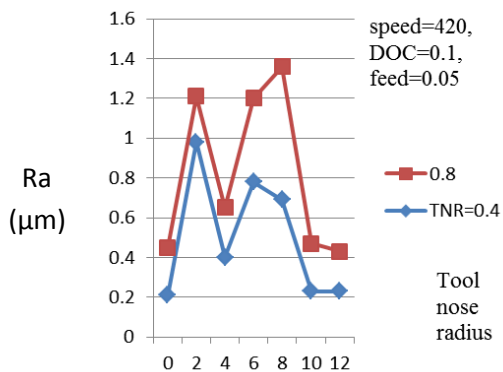


Fig 2: Effect of speed on surface roughness

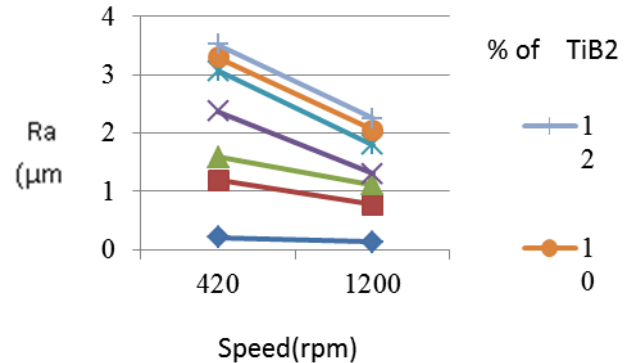


Table 10: Effect of speed on surface roughness

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Toolnose radius	Ra
1	0	420	0.05	0.1	0.4	0.21
2	0	1200	0.05	0.1	0.4	0.13
3	2	420	0.05	0.1	0.4	0.98
4	2	1200	0.05	0.1	0.4	0.64
5	4	420	0.05	0.1	0.4	0.40
6	4	1200	0.05	0.1	0.4	0.34
7	6	420	0.05	0.1	0.4	0.78
8	6	1200	0.05	0.1	0.4	0.19

Table 11: Effect of feed on surface roughness

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Toolnose radius	Ra
1	0	420	0.05	0.1	0.4	0.21
2	0	420	0.11	0.1	0.4	0.7
3	2	420	0.05	0.1	0.4	0.98

4	2	420	0.11	0.1	0.4	1.14
5	4	420	0.05	0.1	0.4	0.40
6	4	420	0.11	0.1	0.4	0.26
7	6	420	0.05	0.1	0.4	0.78
8	6	420	0.11	0.1	0.4	0.76

Table 12: Effect of depth of cut on surface roughness

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Toolnose radius	Ra
1	0	420	0.05	0.1	0.4	0.21
2	0	420	0.05	0.3	0.4	0.55
3	2	420	0.05	0.1	0.4	0.98
4	2	420	0.05	0.3	0.4	0.84
5	4	420	0.05	0.1	0.4	0.40
6	4	420	0.05	0.3	0.4	0.52
7	6	420	0.05	0.1	0.4	0.78
8	6	420	0.05	0.3	0.4	0.81

Fig 3: Effect of feed on surface roughness

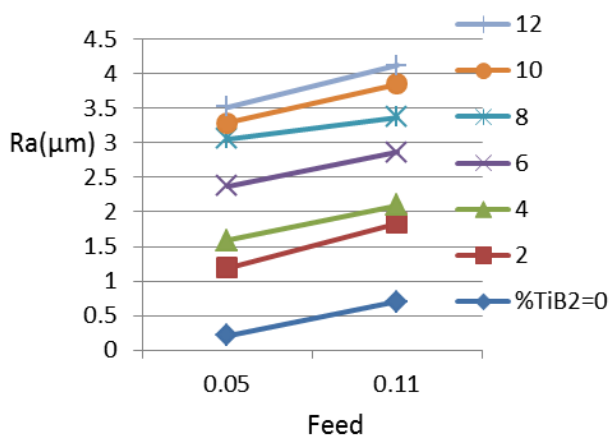


Fig 4: Effect of depth of cut on surface roughness

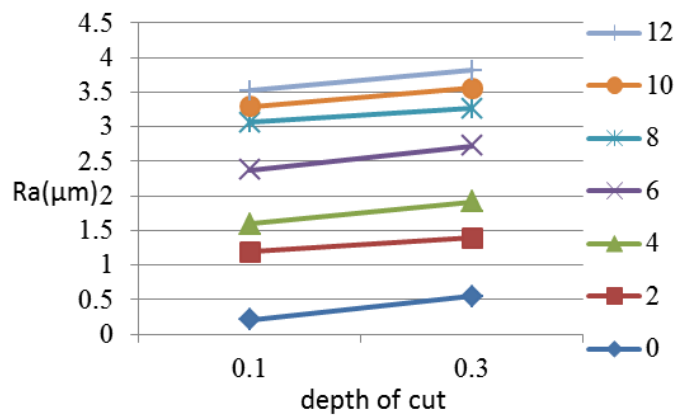


Table 13: Effect of Tool nose radius on surface roughness

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Toolnose radius	Ra
1	0	420	0.05	0.1	0.4	0.21
2	0	420	0.05	0.1	0.8	0.24
3	2	420	0.05	0.1	0.4	0.98
4	2	420	0.05	0.1	0.8	0.23
5	4	420	0.05	0.1	0.4	0.40
6	4	420	0.05	0.1	0.8	0.25
7	6	420	0.05	0.1	0.4	0.78
8	6	420	0.05	0.1	0.8	0.42

Table 14: Comparison of Experimental and predicted Ra when cutting speed is varied

Sample no	%ofTiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	PredictedRa	Error	Relative error
1	2	420	0.05	0.1	0.4	0.98	0.983	0.003	0.305
2	2	1200	0.05	0.1	0.4	0.64	0.75	0.11	14.66

Table 15: Comparison of Experimental and predicted Ra when feed is varied

Sample no	%ofTiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	PredictedRa	Error	Relative error
1	2	420	0.05	0.1	0.4	0.98	1.11	0.13	11.71
2	2	420	0.11	0.1	0.4	1.14	0.99	-0.15	-15.15

Surface Roughness Study on Forged Al-TiB₂ Composite by Regression Analysis

Fig 5: Effect of Tool nose radius on surface roughness

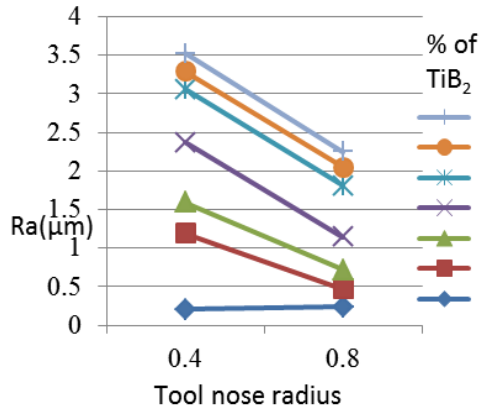


Fig 6: Comparison of Experimental and predicted Ra When Cutting speed is varied

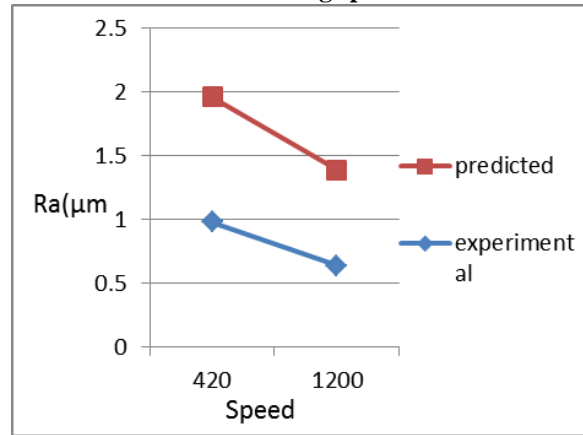


Table 15: Comparison of Experimental and predicted Ra when feed is varied

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	Predicted Ra	Error	Relative error
1	2	420	0.05	0.1	0.4	0.98	1.11	0.13	11.71
2	2	420	0.11	0.1	0.4	1.14	0.99	-0.15	-15.15

Table 16: Comparison of Experimental and predicted Ra when depth of cut is varied

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	Predicted Ra	Error	Relative error
1	2	420	0.05	0.1	0.4	0.98	0.983	0.003	0.305
2	2	420	0.05	0.3	0.4	0.84	0.4	-0.44	11.04

Fig 7: Comparison of Experimental and Predicted Ra when feed is varied

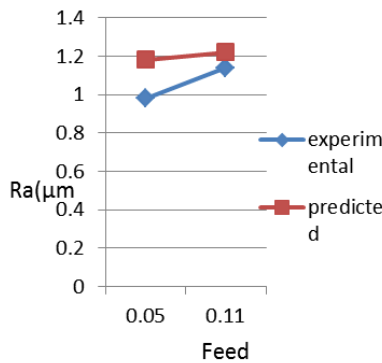


Fig 8: Comparison of Experimental and predicted Ra when depth of cut is varied

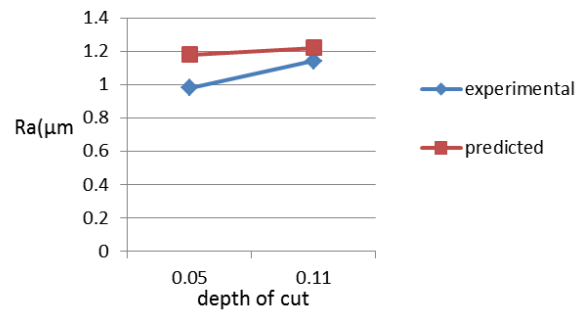


Fig 9: Comparison of Experimental and predicted Ra when Tool nose radius is varied

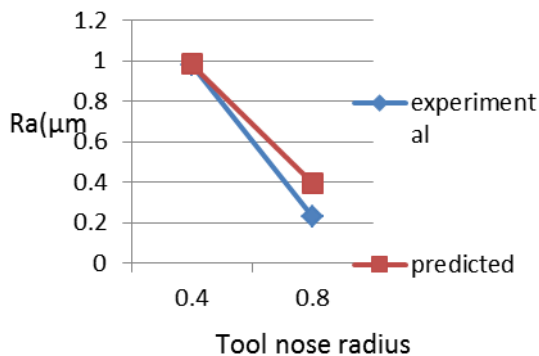


Fig 10: Comparison of Experimental and predicted Ra when %TiB₂ is varied

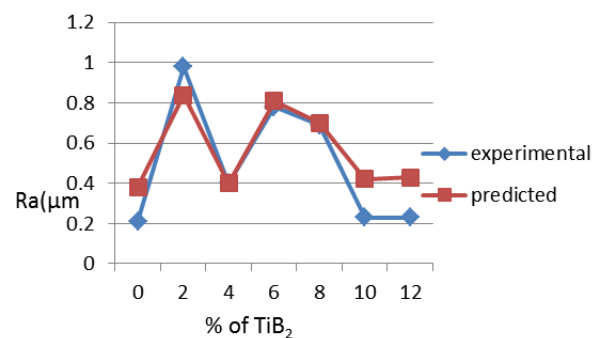


Table 17: Comparison of Experimental and predicted Ra when Tool nose radius is varied

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	PredictedRa	Error	Relative error
1	2	420	0.05	0.1	0.4	0.98	0.983	0.003	0.305
2	2	420	0.05	0.1	0.8	0.23	0.395	0.165	0.041

Table 18: Comparison of Experimental and predicted Ra when %TiB₂ is varied

Sample no	% of TiB ₂ in Al	Speed	Feed	Depth of cut	Tool nose radius	Experimental Ra	PredictedRa	Error	Relative error
1	0	420	0.05	0.1	0.4	0.21	0.38	0.17	44.73
2	2	420	0.05	0.1	0.4	0.98	0.84	-0.14	-0.166
3	4	420	0.05	0.1	0.4	0.40	0.40	0.00	0.00
4	6	420	0.05	0.1	0.4	0.78	0.81	0.03	3.7
5	8	420	0.05	0.1	0.4	0.69	0.70	0.01	1.42
6	10	420	0.05	0.1	0.4	0.23	0.42	0.19	45.23
7	12	420	0.05	0.1	0.4	0.23	0.43	0.20	46.51

V. CONCLUSION:

1. Surface roughness is low at high speed and comparatively high at low cutting speed.
2. Surface roughness increase by increasing feed and decreases by decreasing feed.
3. Surface roughness increase by increasing depth of cut and decreases by decreasing depth of cut.
4. Surface roughness decreases by increasing tool nose radius.
5. Surface roughness is low at low wt% of TiB₂ in aluminum and comparatively high at higher % of TiB₂ in aluminum. However maximum value of surface roughness is observed with 2% TiB₂ composition.
6. The trend of surface roughness predicted by model is similar to the trend obtained by experimental values. However marginal deviations are observed from prediction which may be due to the model prediction accuracy.
7. Hardness of the forged Al-TiB₂ composite increases with wt5% of TiB₂.
8. Irrespective of the percentage composition of TiB₂ surface roughness increases.
9. In many cases it was observed that forged Al-TiB₂ composite had higher surface roughness.

REFERENCES

1. J.E. Allison, G.S. Cole, "metal matrix composite in the automotive industry: opportunities and challenges", JOM (Jan 1993) (19-24).
2. Manna, B. Bhattacharyya, Investigation for effective tooling system to machine Al/SiC-MMC, in: Proceedings of the RAMP-2001, Department of Production Engineering, Annamalai University, India. (465-468).
3. El-Baradie, 1993. Surface roughness model for turning grey cast iron (154). Proc. IMechE, 207:(43-54).
4. Bandyopadhyay, B.P. and E.H. Teo, 1990. Application of factorial design of experiment in high speed turning. (3-8).
5. Gorlenko, O.A., 1981. Assessment of surface roughness parameters and their interdependence. Precis. Eng., #2.
6. K. Manjunath/Optimization and comparative study of cutting parameters for aluminum composite material/MSRIT, Bangalore.
7. M.M.schwartz, "Composites Materials Handbook", Mc Graw Hill Book Co..Pg.1.4-4.131.
8. R.M.Aikini Jr., "The Mechanical Properties of insitu composites".(35-39).

9. J.M.Sanchez, I.Azcona, F.Castro, "Mechanical properties of Titanium Di boride based cements", JOM.Vol.Pg.9-14, 2000.(35-39)
10. Minitab (2000) Meet Minitab, Release 13. Minitab Inc., State College, PA.

