

Synthesis and Effect of TiO₂ on Electrical Conductivity of Poly (2, 5-Dimethoxyaniline)/TiO₂ Thin Film

Maggie Dayana. A, Victor Williams Rayar

Abstract: TiO₂ has been synthesized using Titanium isopropoxide as precursor solution. Different amount of Titanium isopropoxide of 0.2, 0.4, 0.6, 0.8 and 1 mol concentration used to synthesis TiO₂. Different mol concentration solution has been blend with Camphor sulfonic acid protonated Poly (2, 5-dimethoxyaniline) and cast as thin film by dip coating. The optical and XRD analyses were carried out for the dip coated TiO₂ thin films. The DC electrical conductivity was measured for the dip coated Camphor sulfonic acid protonated Poly (2, 5-dimethoxyaniline) /TiO₂ blend thin films. The Titanium isopropoxide of 0.6 mol concentration shows better UV-Vis absorption and crystalline nature. Camphor sulfonic acid protonated Poly (2, 5-dimethoxyaniline) /TiO₂ blend thin film of 0.6 mol concentration shows higher DC electrical conductivity when compared to other mol concentration.

Keywords: Dip coating Poly (2, 5-dimethoxyaniline), thin film, TiO₂, Titanium isopropoxide

I. INTRODUCTION

As simple transition metal oxide, titanium dioxide TiO₂ is a n type semiconductor employed as photo catalysis, optoelectronic devices, memory elements and in cosmetic products[1][2]. TiO₂ possess appreciable transparency, high optical constant and chemical stability [3]. Anatase and Rutile are two phases of TiO₂. The rutile phase is in stabilized state than the anatase phase for range of temperatures [4]. Though many techniques have been preferred for the TiO₂ thin films, like thermal oxidation method [5], sputtering [6], pyrolysis method [7], chemical vapor deposition (CVD) [8] sol-gel[9] is the most accepted method for its own advantageous like uncomplicated, inexpensive and time saving. In this work TiO₂ nano particles are synthesized at different mol concentration of precursor solution using sol-gel dip coating technique to study the electrical property of proton enriched p type Poly(2,5-dimethoxyaniline) /TiO₂ blend thin film. Hybrid material holds the binary properties of organic and inorganic elements[10]. The hybrid material forms a new functional material with the advantages of both the organic and inorganic structures. The organic polymer Poly (2,5-dimethoxyaniline) (PDMA) is a derivative of Polyaniline (Pani) with methoxy group at meta and para position of Pani[11].

The prepared thin films are characterized using UV-Visible spectroscopy, FTIR to find the optimum condition for thin film coating.

II. EXPERIMENTAL PROCEDURE

A. Synthesis of TiO₂ nano particles

Titanium isopropoxide (TTIP-C₁₂H₂₈O₄Ti) was used as precursor solution. Different amount of TTIP (0.2, 0.4, 0.6, 0.8, 1mol) was mixed with 50 ml of anhydrous ethanol (C₂H₅OH) at room temperature under vigorous stirring. After through mixing of solution, 2 ml of distilled water + HCL solution (3:1 ratio) was added. The solutions was kept under stirring for 2 hours to get clear yellow solution. After 12 hours of aging time the solution was obtain proper viscos for coating. Thin films are coated on glass substrate by dip coating for known time. Thin films were allowed for air drying and heated at 150 C for 30 min. Finally films were annealed at 450 C for 1hour.

B. Synthesis of CSA protonated PDMA/ TiO₂ blend thin film

Poly (2, 5-dimethoxyaniline) was synthesized by oxidative polymerization with DMA monomer and Ammonium peroxodisulfate (APS) in 1:1 molar ratio. DMA dissolved in aqueous solution of CSA and keeping the temperature range 0 to 5°C stirred for 30 minutes. For this pre-cooled solution an aqueous solution of APS was added drop by drop until brown color monomer turned into green color solution of CSA protonated Emeraldine Salt (ES) indicating the formation of polymer, PDMA. The solution was stirred for another 5 hours, then filtered using Whatman paper and washed with deionized water to remove the unreacted monomers. The filtered ES - PDMA was dried under open hot air condition for 2 hours. The obtained ES – PDMA was blended with as prepared TiO₂ solutions. Thin films are coated on glass substrate by dip coating method for known time and the thin films are dried under open air condition for 5 hrs.

C. Characterization Techniques

UV-Visible spectrophotometer Perkin Elmer Lambda 35 and FT-IR spectroscopy Perkin Elmer Spectrum RX-1 were used for optical analysis of the thin films. Structural analysis by XRG 3000 X-ray diffractometer (XRD).

Revised Manuscript Received on November 15, 2019

Maggie Dayana, Department of Physics, St. Joseph's college, Tiruchirappalli, India. Email: Maggie.dyna@gmail.com

Victor Williams Rayar Department of Physics, St. Joseph's college, Tiruchirappalli, India.

III. RESULT AND DISCUSSION

A. UV – Visible absorbance spectroscopy

Figure. 1 shows UV – Visible absorbance spectra of TiO₂ thin films coated on glass substrates. All the films are exhibited absorption peak at 380 nm corresponding to the absorption of electrons from VB to CB of titania [12]. With increasing concentration the light absorption is changed and reaches a maximum for 0.6mol concentration. This is due to the formation of titania nanoparticles with good crystalline nature[13]. Thin film coated with 0.8 and 1mol concentration showed decreased light absorption due to the formation of larger sized Titania particles which scattered the light. Thus the increase in concentration not only increase the light absorption but also changes absorption edge towards higher wavelength which is attributed to decrease in band gap energy. Due to the influence of change in morphology of TiO₂ thin film, crystallite size of titania and structural change of TiO₂ phase showed a shift in the wavelength. The band gap value is calculated from the absorption edge and it lies around 3.3 eV which is consistent with reported value.

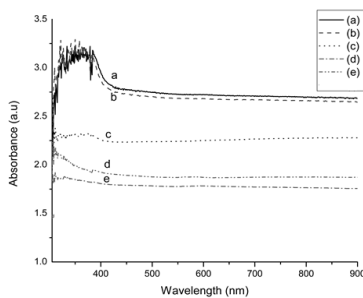


Figure. 1 UV – Visible absorbance spectra of TiO₂ thin films

B. Fourier – Transform Infra-red spectroscopy

Figure. 2 shows FT- IR spectra of synthesized TiO₂ films of different mol concentration of TTIP. The peaks below 1000 cm⁻¹ are due to the Ti-O-Ti stretching and bending vibrational modes and the peak at 1614 cm⁻¹ shows the presence of hydroxyl groups. The well-defined peaks about 400–800 cm⁻¹ with increasing intensity with increase of the mol concentration due to direct Ti-O bonding[14].

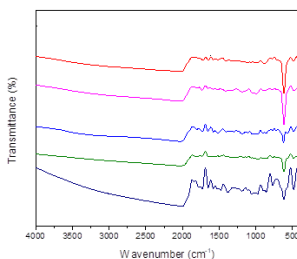


Figure 2. FT-IR spectra of synthesized TiO₂ thin films from 0.2, 0.4, 0.6, 0.8 and 1mol concentration of TTIP (top to bottom).

C. X-Ray Diffraction

Figure 3 shows XRD pattern of TiO₂ thin film. According to standard pattern (JCPDS. NO. 21-1272), the TiO₂ film has pure anatase structure with good crystalline nature. The peaks at 26.50°, 38.95°, 49.17°, 55°, 56.17°, 63.61° and 71.35° are

(101), (004), (200), (105), (211), (204), and (116) planes of anatase titania respectively[15]. The crystallite size is calculated by scherr’s equation $D=0.9 \lambda / \beta \cos (\theta)$ at the characteristic peak 26.50° and it is found to be 24 nm.




Figure 3. XRD pattern of TiO₂ thin film

D. DC electrical conductivity

Electrical conductivity of the pristine and protonated PDMA/TiO₂ thin film coated on a glass substrate was measured in room temperature. Voltage, current and resistance of the thin films have been measured. The specific resistivity of the samples was calculated using the equation

$$\rho = \frac{RA}{l}$$

where R, A and l are the resistance measured,

cross sectional area and the thickness of the film (~1 μm) respectively. The DC electrical conductivity found to be increasing with the Titanium isopropoxide mol concentration of 0.2, 0.4 and 0.6 mol. The EB PDMA shows the value of 1.45 x 10⁻⁷ S/cm. The DC electrical conductivity are found to be 2.7 x 10⁻⁷ S/cm, 3.8 10⁻⁶ S/cm and 5.6 10⁻⁴ S/cm for 0.2, 0.4 and 0.6 mol respectively. Due to the elongation of conjugation length of the polymer and the interaction of TiO₂ withdraws electron due to inductive effect on the polymer backbone leads to increase in conductivity[16][17].

IV. CONCLUSION

In the present work TiO₂ has been synthesized for different mol concentration of Titanium isopropoxide. Different mol solutions has been blend with CSA protonated PDMA and cast as thin film by dip coating. The DC electrical conductivity was measured for dip coated thin film. UV- Vis absorption spectra shows better absorption for 0.6 mol concentration and also better crystalline nature from XRD pattern analysis. The DC conductivity value found to be high for 0.6 mol concentration of TTIP.

REFERENCES

1. A. J. Haider, Z. N. Jameel, and I. H. M. Al-Hussaini, “Review on: Titanium Dioxide Applications,” Energy Procedia, vol. 157, pp. 17–29, 2019.
2. B. Rezaei and H. Mosaddeghi, “Applications of Titanium Dioxide Nanoparticles,” 2009.
3. A. Kusior, J. Banas, A. Trenczek-Zajac, P. Zubrzycka, A. Micek-Ilnicka, and M. Radecka, “Structural properties of TiO₂ nanomaterials,” J. Mol. Struct., vol. 1157, pp. 327–336, 2018.
4. A. V. Raghu, K. K. Karuppanan, and B. Pullithadathil, “Controlled Carbon Doping in Anatase TiO₂ (101) Facets: Superior Trace-Level Ethanol Gas Sensor Performance and Adsorption Kinetics,” Adv. Mater. Interfaces, vol. 6, no. 4, p. 1801714, 2019.
5. T. Narushima, S. Sado, N. Kondo, K. Ueda, M. Kawano, and K. Ogasawara, “Evaluation of Photocatalytic Activity of the TiO₂ Layer Formed on Ti by Thermal Oxidation,” in Interface Oral Health Science 2014, 2015, pp. 65–78.



6. J. Zheng, S. Bao, Y. Guo, and P. Jin, "TiO₂ films prepared by DC reactive magnetron sputtering at room temperature: Phase control and photocatalytic properties," *Surf. Coatings Technol.*, vol. 240, pp. 293–300, 2014.
7. I. Dundar, M. Krichevskaya, A. Katerski, and I. O. Acik, "TiO₂ thin films by ultrasonic spray pyrolysis as photocatalytic material for air purification," *R. Soc. Open Sci.*, vol. 6, no. 2, p. 181578, 2019.
8. V. Bessergenev, I. Khmelinskii, R. J. F. Pereira, V. V. Krisuk, A. Turgambaeva, and I. Igumenov, "Preparation of TiO₂ Films by CVD Method and its Electrical, Structural and Optical Properties," *Vacuum*, vol. 64, pp. 275–279, Jan. 2002.
9. J. M. G. de Salazar, C. N. Duduman, M. J. Gonzalez, I. Palamarciuc, M. I. B. Pérez, and I. Carcea, "Research of obtaining {TiO₂} by sol-gel method using titanium isopropoxide {TIP} and tetra-n-butyl orthotitanate {TNB}," {IOP} Conf. Ser. Mater. Sci. Eng., vol. 145, no. 7, p. 72011, Aug. 2016.
10. Y. Chujo, "Organic–inorganic hybrid materials," *Curr. Opin. Solid State Mater. Sci.*, vol. 1, no. 6, pp. 806–811, 1996.
11. V. Patil, S. R. Sainkar, and P. P. Patil, "Growth of poly(2,5-dimethoxyaniline) coatings on low carbon steel," *Synth. Met.*, vol. 140, no. 1, pp. 57–63, 2004.
12. "Modified TiO₂ based photocatalysts for improved air and health quality," *J. Mater.*, vol. 3, no. 1, pp. 3–16, 2017.
13. M. Koelsch, S. Cassaignon, J. F. Guillemoles, and J. P. Jolivet, "Comparison of optical and electrochemical properties of anatase and brookite TiO₂ synthesized by the sol–gel method," *Thin Solid Films*, vol. 403–404, pp. 312–319, 2002.
14. Z. N. Jameel, A. Haider, and Y. Taha, "Synthesis of TiO₂ Nanoparticles by Using Sol-Gel Method and its Applications as Antibacterial Agents," 2013.
15. W. Li, R. Liang, A. Hu, Z. Huang, and Y. Zhou, "Generation of oxygen vacancies in visible light activated one-dimensional iodine TiO₂ photocatalysts," *RSC Adv.*, vol. 4, Aug. 2014.
16. Y. Li, H. Ban, H. Zhao, and M. Yang, "Facile preparation of a composite of TiO₂ nanosheets and polyaniline and its gas sensing properties," *RSC Adv.*, vol. 5, no. 129, pp. 106945–106952, 2015.
17. Q. Wang, X. Dong, Z. Pang, Y. Du, X. Xia, Q. Wei, and F. Huang, "Ammonia sensing behaviors of TiO₂-PANI/PA6 composite nanofibers," *Sensors (Switzerland)*, vol. 12, no. 12, pp. 17046–17057, 2012.

AUTHORS PROFILE



Maggie Dayana pursuing Phd . Interested in thin films, polymer thin film for gas sensing application.



Dr. Victor Williams Rayar was Professor of Physics at St. Joseph's college (Autonomous), Tiruchirappalli He has published more than twenty five research articles in reputed International Journals. He has attended many National and International conferences and delivered invited talks. He has specialised himself in thin film physics, solar energy and instrumentation techniques.