

Effect of Admixing Fly Ash on Cementing Characteristics of Magnesium Oxychloride Cement

Rekha Sharma, R. N. Yadav



Abstract: Investigations pertaining to the effect of admixing different amounts of fly ash on setting characteristics and compressive strength of magnesium oxychloride cement has been carried out in this paper. For this purpose, two different dry mix compositions (1:0 and 1:1) of magnesia and dolomite were prepared and 5 %, 10 %, 15 % and 20 % fly ash were added in dry mixes. The dry mixes were then gauged with 24 °Be concentration of magnesium chloride gauging solution. It was observed that initial and final setting times of cement blocks tend to increase with increasing amount of fly ash in dry mix. MOC cement blocks of 1:1 composition admixed with fly ash displayed good cementing characteristics.

Keywords: Compressive strength, fly ash, Gauging solution, Inert filler, MOC, Setting time.

I. INTRODUCTION:

Magnesium oxychloride cement is an inorganic mineral binder which was introduced by a French chemist S. T. Sorel in 1867 [1]. It is prepared via an exothermic reaction between reactive MgO powder and concentrated MgCl₂. At room temperature phase-3 or [3Mg(OH)₂.MgCl₂.8H₂O] and phase-5 or [5Mg(OH)₂.MgCl₂.8H₂O] are the two chief hydrated phases that impart mechanical strength to the cement by intergrowth and interlocking tendencies of their needle like crystals [2]-[5]. This cement displays some very unique and diverse cementing properties that renders it superior in comparison to Portland cement, as reported by several researchers [6]-[10]. Due to very low specific gravity (~2.4), it is resilient and light in weight. It acts as a tough stone like, fire proof compound which is extensively used for both light and heavy floorings. MOC cement is characterized by rapid setting and high early strength. After setting it does not require humid curing. Owing to the low value of thermal expansion coefficient, it displays negligible volume changes during setting. MOC cement is also characterized by higher compressive strengths ranging in between 9000-45000 psi and tensile strength of over 800 psi as compared to conventional concrete [11]..

Manuscript received on January 20, 2021.
Revised Manuscript received on January 24, 2021.
Manuscript published on January 30, 2021.

* Correspondence Author

Mrs. Rekha Sharma*, Department of Chemistry, Govt. RR (PG) College, Alwar 301001, India. Email: rsrekh19@gmail.com

Dr. R. N. Yadav, Department of Chemistry, Govt. RR (PG) College, Alwar 301001, India. Email: yadavrama62@yahoo.co.in

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](#) article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>)

Magnesium oxychloride cement possesses enormous load bearing capacity and can easily resist vibrations arising from heavy cast iron wheels, without displaying any cracks or fissures [5]. It shows better resistance towards oil, grease and paints and remains unaltered by the attack of acids or alkalis

It is resistant to abrasion also. Owing to its lower pH value (10-11) as compared to Portland cement with pH value (12-13), it could be used conveniently with fiber glass without causing aging problems [12].

The manufacturing process of MOC binders is not only free from any carbon dioxide gas emissions, but due to carbon sequestration potential, these binders actually act as "sinks" for atmospheric carbon dioxide [13]. The important commercial applications of MOC binders include floorings of industries and hospitals, grinding wheels and wall insulation panels due to its marble like gloss. The industrial applications of MOC cement has been limited because of the associated problems of poor water resistance, volume instability, cracking and sweating etc. The magnesium oxychloride binder system exhibits excellent bonding capacity to a large variety of organic and inorganic substances. Different additives such as fillers, fibers, metals, wood, plastic, rubber, glass and even waste materials such as fly ash [14], granite [15] and asbestos wastes [16] etc. have been incorporated in it to get the desired properties in MOC binders. Effect of various additives on setting, strength and water resistance of magnesia cement has been studied by different researchers [8], [9], [14], [17]- [19]. Fly ash is a waste byproduct generated in coal based thermal power plants in huge amounts every year. The power plant ashes (or coal ashes) are generated as a mixture of coarse bottom ash (20 %) or finer pozzolanic fly ash (80 %) or flue ash. The word "pozzolanic" refers to the capacity of fly ash to react with lime and water at room temperature to form a water insoluble, solid cement like substance [20]. In cement and concrete technology, fly ash is defined as "pulverized fuel ash" [21]. The ministry of power, government of India estimates 1800 million tons of coal use every year and 600 million tons of fly ash generation by the year 2031-32 [22]. This surplus fly ash stock is posing a great threat in terms of precious land required for its disposal, detrimental impacts on environment and its inherent potential to cause health hazards. Hence in present scenario, the safe management and substantial utilization of this surplus fly ash generated, has become a major challenge. In recent years the intrinsic worth of fly ash for applications in diverse areas has been acknowledged.

Effect of Admixing Fly Ash on Cementing Characteristics of Magnesium Oxychloride Cement

Construction industry is one such area which has a large potential to incorporate fly ash. Admixing of fly ash in concrete renders it an eco-friendly and energy efficient building material as it leads to a reduction in carbon footprint of concrete [14]. This addition also extends technical benefits of concrete, reduces its cost, saves virgin raw materials (coal, limestone etc.) and precious land resources required for fly ash disposal [22] - [23]. On the other hand, considering environmental concerns this incorporation of fly ash into concrete serves for an efficient method for its safe disposal and sustainable utilization. As a result, fly ash earlier considered as "hazardous waste material" is now being treated as "valuable resource material and saleable commodity" [21].

II. MATERIALS AND METHODS:

The raw materials used in the study were calcined magnesite, magnesium chloride, dolomite powder and fly ash.

A. Calcined Magnesite

Magnesia used in this study was of Salem, Chennai origin with following characteristics: (1) Bulk density 0.85 kg /l (2) 95 % passing through 75-micron (200 IS sieve) (3) minimum magnesium oxide 90 % (4) CaO < 1.5 % (5) Ignition loss at 100 °C~ 2.5 ± 0.5 %.

B. Magnesium Chloride ($MgCl_2 \cdot 6H_2O$)

Magnesium chloride used in present study was of Indian Standard Grade 3 of Indian Standard: 254-1973 with following characteristics: (1) Colorless, crystalline, hygroscopic crystals. (2) Highly water soluble. (3) Magnesium chloride hexahydrate minimum 95 % (4) Magnesium sulphate, calcium sulphate and alkali chlorides (NaCl) contents < 4%.

C. Dolomite (Inert Filler)

Dolomite dust was used as an inert filler having following grading: (1) 100 % passing through 200-micron Indian Standard sieve (2) 50 % retained on 125-micron IS sieve (3) CaO ~ 28.7 % (4) MgO ~ 20.8 % (5) Insoluble and other sesquioxide contents < 1.0 %.

D. Fly Ash (Additive)

Fly ash was procured from Dadri thermal power plant, Uttar Pradesh. It had following characteristics: (1) SiO_2 - 62.58 % (2) Fe_2O_3 - 13.50 % (3) Al_2O_3 - 8.50 % (4) CaO - 1.68 % (5) MgO - 1.60 % (6) Na_2O - 0.18 % (7) K_2O - 0.21 % (8) SO_3 - 9.00 % (9) LOI - 1.45 %.

Physical Characteristics- (1) Whiteness - 43.30 % (2) oil absorption – 26.20 ml /gm (3) water absorption – 33.80 % (4) pH - 7.20 (5) bulk density- 1.11 gm /cc (6) moisture- 0.06 %.

E. Preparation of magnesium chloride solution

Magnesium chloride solution was prepared by transferring magnesium chloride flakes into plastic containers and then adding potable water to it to obtain concentrated solution. This solution was kept overnight to allow insoluble impurities to settle down at the bottom. The supernatant concentrated solution was then transferred into other plastic container and well stirred after each dilution prior to the determination of specific gravity. Concentration of the

solution is expressed in terms of specific gravity on Baume scale (Be).

F. Preparation of dry-mix compositions

Dry mixes were prepared by mixing lightly calcined magnesite (magnesia) and dolomite (inert filler) in the ratio 1:0 and 1:1 by their weight and then admixing fly ash in different amounts (5 %, 10 %, 15 % and 20 %) in each dry mix composition.

G. Determination of Standard consistency and setting times of cement pastes

Wet mixes were prepared by gauging dry mix composition with 24 °Be magnesium chloride gauging solution. The standard consistency, initial and final setting times were investigated as per IS 10132-1982 using Vicat apparatus [24]- [26]. The observed results are displayed in table-I and table-II.

H. Determination of Compressive strength

Influence of admixing fly ash on compressive strength of MOC cement was determined by using cubes (molds) of size $70.6 \times 70.6 \times 70.6$ mm³ as per standard procedure [5], [25], [27]. Dry-mix compositions were prepared by mixing magnesia and dolomite in 1:0 and 1:1 ratio by their weight and adding 5 %, 10 %, 15 % and 20 % fly ash additive in dry-mix. These dry mixes were then gauged with 24 °Be gauging solution. All cubes were air dried at room temperature under lab conditions (75 ± 5 % relative humidity, 30 ± 2 °C temperature) and were tested for compressive strength after 30 days. The results obtained are recorded in table-III and table-IV.

I. Determination of Durability

To determine the durability of product, Le-Chateliers test was conducted as per the standard procedure [18], [24] and the results are recorded in table-V and table-VI.

III. RESULTS AND DISCUSSION

The effects of adding fly ash as an admixture, on setting characteristics of magnesium oxychloride cement having different dry mix compositions are displayed in table-1 and table-11 (fig. 1 and 2).

Table 1: Effect of fly ash on setting characteristics of 1:0 dry-mix composition of MOC.

Fly Ash (%)	Without FA	5 % FA	10 % FA	15 % FA	20 % FA
MgCl₂ / Gauging Solution (ml)	94	92	91.5	90	88
IST (min.)	72	82	87	93	98
FST (min.)	210	225	236	250	262

Concentration of Gauging Solution: 24 °Be, Dry mix: 1:0*
Humidity: 75 ± 5 %



* One part by weight of magnesia and no dolomite
 IST: Initial setting time; FST: Final setting time, FA: Fly Ash

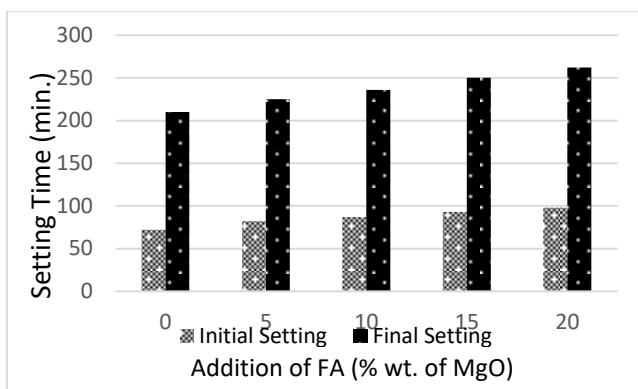


Fig 1: Effect of fly ash on setting time of 1:0 dry mix of MOC.

It is quite evident that if the amount of magnesia in 1:0 dry mix is replaced by dolomite, as in dry mix (1:1), setting time tends to increase. This can be related to the nature of dolomite, an inert filler incorporated in the dry mix composition, which has a tendency to retard the evolution of heat (or exothermicity). For different compositions of wet mix, the increasing tendency of setting time may also be attributed to the property of crystalline phases present in the cement paste. Thus, the coupled effect of two factors, increasing amount of inert filler content and decreasing rate of heat evolution determines the observed trends. Final setting times are also following the same trend (table I-II, fig. 1-2). It was also observed that both setting times increased with increasing amount of fly ash.

Table II: Effect of Fly ash on setting characteristics of 1:1 dry-mix composition of MOC.

Concentration of Gauging Solution: 24 °Be, Dry mix: 1:1*
 Humidity: 75 ± 5%

Fly Ash (%)	Without FA	5 % FA	10 % FA	15 % FA	20 % FA
MgCl ₂ / Gauging Solution (ml)	80	77.5	76.5	75	74
IST (min.)	90	102	111	120	130
FST (min.)	230	250	265	282	300

* One part by weight of magnesia and one part by weight of dolomite

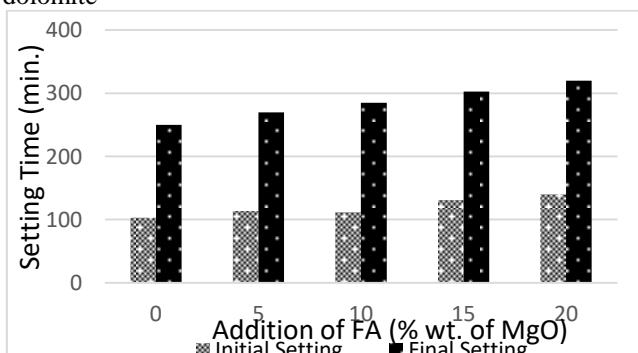


Fig 2: Effect of fly ash on setting time of 1:1 dry mix of MOC. IST: Initial setting time; FST: Final setting time, FA: Fly ash

The small and spherical shaped fly ash particles reduce particle friction by exerting lubricating effect. This causes an increase in the fluidity (or workability) of the wet mix [29]- [30]. As a result, setting times tend to increase.

The results recorded in table I-II show the volume of gauging solution required for standard consistency. It was observed that volume of gauging solution required for standard consistency at different compositions of the dry mix (1:0 and 1:1) tends to decrease almost uniformly. Although dry-mix 1:0 requires more amount of gauging solution than dry-mix 1:1. The two factors, increasing inert filler content and amount of heat evolved are collectively responsible for the observed trends. Similarly, in each dry-mix composition, the amount of gauging solution decreases with increasing amount of fly ash. This can be related to the spherical shape of fly ash particles that lower particle friction and exert lubricating effect. This results in reduced water demand and improved workability (or fluidity) of the wet mix. Investigations pertaining the effect of fly ash admixture on compressive strength of MOC samples prepared with different dry mix compositions and gauged with 24 °Be concentration of gauging solution are summarized in the table III-IV and figure 3-4.

Table III: Effect of Fly ash on compressive strength of 1:0 dry-mix composition of MOC.

Fly Ash (%)	Without FA	5 % FA	10 % FA	15 % FA	20 % FA
Load (Kg/N)	300	255	260	275	285
Compressive Strength (MPa)	60.188	51.16	52.163	55.173	57.179

Concentration of Gauging Solution: 24 °Be Dry mix: 1:0*
 Humidity: 75 ± 5 % * One part by weight of magnesia and no dolomite. FA: Fly Ash

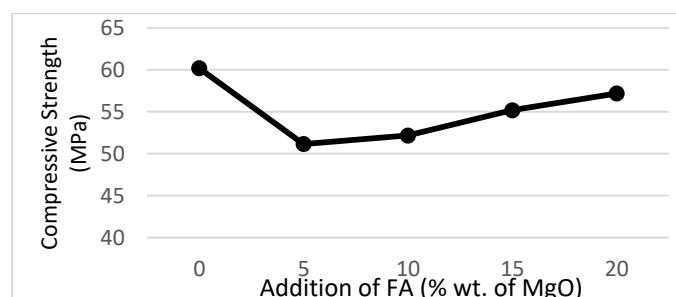


Fig. 3: Effect of Fly ash on compressive strength of 1:0 dry-mix composition of MOC.

In case of 1:0 dry mix (table III, fig. 3) gauged with 24 °Be of gauging solution, it was observed that addition of fly ash initially lowers the strength as compared to control block (without fly ash). The compressive strength for 5 % addition of fly ash is 51.160 MPa (255 Kg/N) which is lower than the strength of control mix 60.188 MPa (300 Kg /N). As the amount of fly ash addition is increased strength also increases gradually.



Effect of Admixing Fly Ash on Cementing Characteristics of Magnesium Oxychloride Cement

For 15 and 20 % fly ash addition strength achieved is 55.173 MPa (275 Kg /N) and 57.179 MPa (285 Kg /N) respectively.

This may be attributed to the fact that only magnesia is present in 1:0 dry mix, which reacts with magnesium chloride gauging solution to form strength giving phase-5. Incorporation of fly ash serves for dual role for strength development. The excess lime, released during hydration of cement, acts as a source for fly ash pozzolanic reaction and generates additional C-S-H gel having binding properties similar to that produced by hydration of cement paste. This reaction of fly ash with excess lime continues as long as lime is present in the pores of wet mix and imparts additional strength to it. On the other hand, the unreactive portion of fly ash behaves as "micro-aggregates" and fills up the matrix. This leads to enhanced packing effect and strength of cement [29]-[31]. Hence strength increases with increasing amount of fly ash.

In case of 1:1 dry mix composition (table IV, fig. 4) a decrease in strength was observed with initial addition of fly ash. The compressive strength of cement for 5 % addition of fly ash is 49.154 MPa (245 Kg /N) which is lower than the strength of control mix 58.182 MPa (290 Kg /N). Then it increased and maximum strength of 54.169 MPa (270 Kg /N) was obtained for 10 % addition of fly ash. After this strength reduced slightly with further addition of fly ash. Although strength obtained was higher than 45 MPa in all cases. For 15 % and 20 % fly ash addition strength obtained were 52.163 MPa (260 Kg /N) and 46.144 MPa (230 Kg /N) respectively. In 1:1 dry mix magnesia content is replaced by inert filler dolomite powder which is a double carbonate of calcium and magnesium. During the preparation of wet mixes, it gets converted into its respective oxides and expels

carbon dioxide. Hence, compressive strength of molds reduces accordingly as the amount of inert filler increases in dry mixes of MOC samples.



Table IV: Effect of Fly ash on compressive strength of 1:1 dry-mix composition of MOC.

Fly Ash (%)	Without FA	5 % FA	10% FA	15 % FA	20 % FA
Load (Kg/N)	290	245	270	260	230
Compressive Strength (MPa)	58.182	49.154	54.169	52.163	46.144

Concentration of Gauging Solution: 24 °Be Dry mix: 1:1*
Humidity: 75 ± 5 %

* One part by weight of magnesia and one part by weight of dolomite. FA: Fly Ash

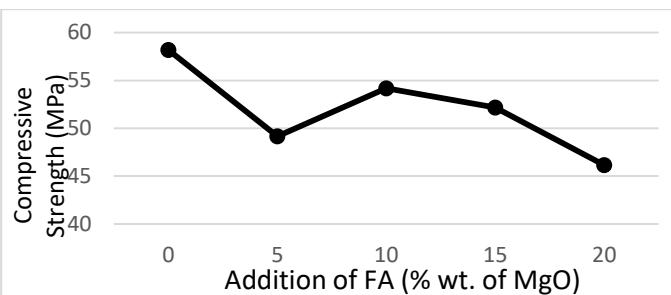


Fig 4: Effect of Fly Ash on Compressive Strength (MPa) of 1:1 Dry Mix Of MOC.

Table V: Effect of Fly ash on soundness of 1:0 dry-mix composition of MOC.

S. No.	Observations	Without FA	With 5% FA	With 10% FA	With 15% FA	With 20% FA
1	Weight of cement composition (gm)	38	38	38	38	38
	(i) Magnesia	38	36.1	34.2	32.3	30.4
	(ii) Dolomite	-	-	-	-	-
	(iii) Fly ash	-	1.9	3.8	5.7	7.6
2	Amount of MgCl ₂ solution (in ml)	19.5	18.5	18.2	18	17.5
3	Distance between two pointers before starting (in mm)	9	11	14	8	10
4	Distance between two pointers after 7 days before boiling (in mm)	12	14	16	10	12
5	Distance between two pointers after boiling (in mm)	13.5	15.5	17	11	13
6	Expansion of cement (in mm)	1.5	1.5	1	0.5	0.5

Concentration of Gauging Solution: 24 °Be

Dry-mix: 1:0*

Humidity: 75 ± 5 %

* One part by weight of magnesia and no dolomite., FA: Fly Ash The results of fly ash addition on durability of 1:0 and 1:1 dry mix of MOC has been recorded in table-V and table-VI. It was observed that in case of 1:0 dry mix expansion of molds decreases (or soundness improves) with increasing amount of fly ash (table V). When magnesia content in MOC cement is replaced by inert filler dolomite,

as in 1:1 dry mix composition (table VI), the expansion in the volume of trial blocks tends to increase in comparison to 1:0 dry mix with no dolomite.



When fly ash is admixed expansion first increases and then reduces slightly for higher amounts of fly ash. The most plausible explanation of this trend is the fact that when ratio of inert filler increases in dry mix composition, the amount of residual active lime and unreacted magnesia content in the matrix also increases. These unconsumed contents undergo hydration during soundness test and cause volume expansion by converting into their respective hydroxides. Thus, positive volume changes are quite obvious under humid conditions.



On boiling the trial blocks, active lime and magnesia are formed by the decomposition of inert filler dolomite with the expulsion of carbon dioxide. Hence under humid conditions significant volume changes are observed due to the formation of calcium and magnesium hydroxides. When fly ash is admixed in concrete, these alkalis are consumed by the reaction occurring between the siliceous glass of fly ash and the alkali hydroxide of the cement paste. Hence, their availability for causing expansion reaction with reactive aggregates is reduced. Also, when cementitious material is partly replaced by fly ash, amount of heat evolution is low. This liberated heat is consumed during pozzolanic reaction of fly ash. As a result, micro-cracking is reduced with increased soundness of cement binders.

Table VI: Effect of Fly ash on soundness of 1:1 dry-mix composition of MOC.

S. No.	Observations	Without FA	With 5% FA	With 10% FA	With 15% FA	With 20% FA
1	Weight of cement composition (gm)	38	38	38	38	38
	(i) Magnesia	19	18.05	17.1	16.2	15.2
	(ii) Dolomite	19	19	19	19	19
	(iii) Fly ash	-	0.95	1.9	2.8	3.8
2	Amount of MgCl ₂ solution (in ml)	14.5	14.5	14	13.5	13
3	Distance between two pointers before starting (in mm)	12	11	8	7	14
4	Distance between two pointers after 7 days before boiling (in mm)	16	15	11	10	17
5	Distance between two pointers after boiling (in mm)	18.5	18	13.5	12	19
6	Expansion of cement (in mm)	2.5	3	2.5	2	2

Concentration of Gauging Solution: 24 °Be

Dry-mix: 1:1*

Humidity: 75 ± 5%

* One part by weight of magnesia and two parts by weight of dolomite. FA: Fly Ash

IV. CONCLUSION

- (1) Admixing of fly ash in 1:0 and 1:1 dry-mix compositions improves workability of the wet mix.
- (2) Dry mix compositions (1:0 and 1:1) display similar trends for increase in setting time characteristics by incorporation of fly ash. Although setting times are prolonged in presence of dolomite.
- (3) Dry mix composition 1:1 (equal amounts of magnesia and dolomite) with incorporation of fly ash also exhibits good cementing characteristics such as compressive strength and durability.
- (4) Thus 1:1 dry mix composition has a potential to be used as a cost-effective cementing material.

ACKNOWLEDGMENT

We are thankful to Dr. H. Singh, principal R. R. College, Alwar for providing lab facilities in college. We are also

thankful to K. Jain of PWD, Alwar for providing facilities for compressive strength measurements.

REFERENCES

1. S. T. Sorel, "A New Magnesium Cement." *Comp Rend*, 65, 1867, 102-104.
2. C. A. Sorrel, and C. R. Armstrong, "Reactions and equilibria in magnesium oxychloride cements." *I. Am. Ceram. Soc.*, 59, 1976, 51-54.
3. Z. Li, and C. K. Chau, "Influence of fly ash on properties of magnesium oxychloride cement." *Cement Concrete Res.*, 37(6), 2007, 866-870.
4. A. K. Mishra, and R. Mathur, "Magnesium Oxychloride Cement Concrete." *Bull. Mater. Sci.*, 30 (3), 2007, 239-246.
5. R. Mathur, (1986). "Effect of temperature of calcination of magnesite and proportion of inert fillers on the bonding characteristics of magnesium oxychloride cement." (Ph.D. thesis), University of Rajasthan, Jaipur, India



Effect of Admixing Fly Ash on Cementing Characteristics of Magnesium Oxychloride Cement

6. J. J. Beaudoin, and V. S. Ramachandran, "Strength development in magnesium oxychloride and other cements." *Cement and Concrete Research*, 5(6), 1975, 617-630.
7. J. J. Beaudoin, V. S. Ramachandran, and R. F. Feldman, "Impregnation of Magnesium Oxychloride Cement with Sulfur." *Am. Ceram. Soc. Bull.*, 424 (1977).
8. M. P. S. Chandrawat, and R. N. Yadav, "Effect of aluminum phosphate as admixture on oxychloride cement." *Bull. Mater. Sci.*, 23, 2000, 69-72.
9. M. P. S. Chandrawat, T. N. Ojha, and R. N. Yadav, "Effect of bitumen emulsion on setting, strength, soundness and moisture resistance of oxychloride cement." *Bull. Mater. Sci.*, 24 (3), 2001, 313-316.
10. M. P. S. Chandrawat, R. N. Yadav, P. Gupta, and N. Dagur, "Impact of sodium silicate as an additive on the properties of MOC cement." *Int. J. Chem. Sci.*, 9 (2), 2011, 581-588.
11. G. Swanson, Building Biology Based New Building Protocol Magnesium Oxide, Magnesium chloride and Phosphate - based Cements. History of magnesia cement, 28 march 2011 by Admin on HONU Board A HONU way of building future.
12. V. M. Sglavo, F. De Genua, A. Conci, R. Ceccato, and R. Cavallini, "Influence of curing temperature on the evolution of magnesium oxychloride cement." *J. Mater. Sci.*, 46, 2011, 6726-6733. (DOI 10.1007/s10853-011-5628-z0)
13. I. M. Power, G. M. Dipple, and P. S. Francis, "Assessing the carbon sequestration potential of MOC cement building materials." *Cement Concrete Comp.*, 78, 2017, 97-107. (Doi 10.1016/j.cemconcomp.2017.01.003)
14. C. K. Chau, J. Chan, and Li Zongjin, "Influence of fly ash on magnesium oxychloride mortar." *Cement and Concrete composites*, 31 (4), 2009, 250-254.
15. Y. Li, H. Yu, L. Zheng, J. Wen, C. Wu and Y. Tan, "Compressive strength of fly ash magnesium oxychloride cement containing granite wastes." *Constr Build Mater.*, 38, 2013, 1-7. (Doi 10.1016/j.conbuildmat.2012.06.016)
16. R. Kusiorowski, T. Zaremba, "The use of asbestos wastes as fillers on sorel cement." *Ceram Silicaty.*, 62(1), 2018, 31-40. (Doi: 10.13168/cs.2017.0042)
17. Y. K. Gupta, M. P. S. Chandrawat, R. N. Yadav, "Effect of Glycerol in Setting, Strength and Moisture Resistance of Oxychloride Cement (Sorel's cement)." *Res. and Ind.*, 35, 1990, 191.
18. Y. K. Gupta, M. P. S., Chandrawat, and R. N. Yadav, "Effect of Magnesium Sulphate in Setting, Strength and Moisture Resistance of Oxychloride Cement." *Proc. NASIA*, 64 (A) II, 1994, 2000.
19. M. P. S. Chandrawat, R. N. Yadav, and R. Mathur, "Effect of Disodium Hydrogen Phosphate on Some Properties of Magnesia Cement." *Res. and Ind.*, 39 (1), 1994, 18-21.
20. Fly ash Wikipedia, the free encyclopedia. (https://en.wikipedia.org/wiki/Fly_ash).
21. Report on Fly Ash Generation at Coal / Lignite Based Thermal Power Stations and its Utilization in the Country for the year 2018-19.
22. Y. Singh, "Fly Ash Utilization in India." The Wealthy Waste School, India. (2017). (www.wealthywaste.com > fly-ash utilization).
23. M. Kr. Tiwari, "Fly Ash Utilization: A Brief Review in Indian Context." *International Research Journal of Engineering and Technology*, 3(4), 2016, 949-956.
24. B. L. Gupta, "Concrete Technology," (New Delhi: Standard Publisher), (1976), pp 18.
25. Methods of Test for Materials for Use in the Preparation of Magnesium Oxychloride Flooring Composition, Indian Standard Institution, (1982).
26. P. Gupta, "Effect of temperature and concentration of gauging solution on setting, strength, durability and bonding characteristics of magnesium oxychloride cement (MOC)." (Ph.D. Thesis), (2012), Jaipur, Rajasthan, University of Rajasthan.
27. R. N. Yadav, "Effect of some additives on setting, strength and moisture resistance of oxychloride cement." (Ph.D. Thesis), 1989, Jaipur, Rajasthan, University of Rajasthan.
28. I. Nawaz, "Disposal and Utilization of Fly to Protect the Environment." *International Journal of Innovative Research in Science, Engineering and Technology*, 2(10), 2013, 5259-5266.
29. O. K. Wattimena, Antoni, and D. Hardijito, "A review on the effect of fly ash characteristics and their variations on the synthesis of fly ash based geopolymers." AIP Conference Proceedings 1887, 020041, (2017). (Doi 10.1063/1.5003524)
30. "Fly Ash for Cement Concrete." - Book published by Ash Utilization Division of NTPC, 2007, 9-12.
31. S. K. Bremseth, "Fly ash in concrete-A literature study of the advantages and disadvantages". COIN project report 18-2010, SINTEF building and infrastructure.

AUTHORS PROFILE



Mrs. Rekha Sharma is currently working as an Associate Professor in Department of Chemistry at R. R. Government College, Alwar (Rajasthan). She is actively involved in teaching UG and PG classes from past 22 years. Her area of specialization is organic chemistry. She is keenly interested in research and academics.



Dr. R. N. Yadav is working as an Associate Professor in Department of Chemistry at R. R. Government College, Alwar (Rajasthan). He pursued his Ph. D degree in Chemistry from University of Rajasthan, Jaipur. He is actively engaged in research work and has contributed more than 40 publications in various national and international journals, conferences of repute. He has successfully accomplished several UGC sanctioned projects (5-minor and 2-major). Dr. Yadav has actively organized a state level seminar on fluoride and national conference on green chemistry and water technology.